

Packaging Materials and Design for Improved PV Module Reliability

G. Jorgensen, K. Terwilliger, M. Kempe, J. Pern,
S. Glick, J. del Cueto, C. Kennedy, and
T. McMahon

*Presented at the 2004 DOE Solar Energy Technologies
Program Review Meeting
October 25-28, 2004
Denver, Colorado*

Conference Paper
NREL/CP-520-36835
January 2005

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy
and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>



Printed on paper containing at least 50% wastepaper, including 20% postconsumer waste

Packaging Materials and Design for Improved PV Module Reliability

G. Jorgensen, K. Terwilliger, M. Kempe, J. Pern, S. Glick, J. del Cueto, C. Kennedy, T. McMahon
National Renewable Energy Laboratory
1617 Cole Blvd., Golden, CO 80401
Gary_Jorgensen@NREL.GOV

ABSTRACT

A number of candidate alternative encapsulant and soft backsheets materials have been evaluated in terms of their suitability for photovoltaic (PV) module packaging applications. Relevant properties, including peel strength as a function of damp heat exposure and permeability, have been measured. Based on these tests, promising new encapsulants with adhesion-promoting primers have been identified that result in improved properties. Test results for backsheets provided by industry and prepared at the National Renewable Energy Laboratory (NREL) have suggested strategies to achieve significantly improved products. The ability of glass/glass and glass/breathable backsheet constructions laminated with various encapsulant and/or edge seal materials to protect thin-film aluminum coatings deposited onto glass substrates was assessed. Glass/glass laminate constructions can trap harmful compounds that catalyze moisture-driven corrosion of the aluminum. Constructions with breathable backsheets allow higher rates of moisture ingress, but also allow egress of deleterious substances that can result in decreased corrosion.

1. Objectives

Improved packaging materials are required to increase reliability of thin-film PV modules. As discussed in the Solar Program Multi-Year Technical Plan [1], a major impediment for flat-plate PV systems is the limitation in cost and reliability of module packaging. Both crystalline-silicon and thin-film technologies require advanced module packaging to survive in harsh operating environments. The objective of this research is to identify new, cost-effective packaging materials that demonstrate improved moisture barrier and adhesion properties with weathering. Candidates include both commercial and experimental materials provided by the private sector, and experimental materials developed in-house.

2. Technical Approach

A number of new encapsulants and backsheets have been evaluated as improved packaging materials. The primary properties of interest were adhesion (using an Instron 5500R mechanical testing unit) as a function of damp heat exposure and moisture transport (measured with a Mocon Permatran-W 3/31 instrument). Peel strength measurements (both 90° and 180°) have been made to allow screening of alternate encapsulant formulations and to test the durability of interfacial adhesion. By measuring the time-dependent permeability of backsheets and encapsulants, the diffusivity and solubility of these materials can be derived and used to

compute moisture ingress time scales [2]. Finally, the ability of combinations of packaging components to protect PV devices from corrosion was assessed.

3. Results and Accomplishments

3.1 Encapsulants

Candidate encapsulants were compared with a control material, namely, a standard fast-cure ethylene vinyl acetate (EVA) product (designated 15295P) from Specialized Technology Resources, Inc. (STR). Samples included silicones and primers from GE and Dow Corning, an experimental material from BRP Manufacturing (BRP-C), an experimental fluorocarbon from Saint-Gobain (THV), and several in-house formulations.

A number of silane adhesion promoters designed to improve adhesion of EVA to glass were screened by priming the glass substrates and preparing samples at NREL. Their construction was: Tedlar-Polyethylene Terephthalate (PET)-EVA (TPE)/EVA/primed glass. The 90° peel strength was measured between EVA and glass as a function of damp heat exposure. Some samples were found to have a statistically significant improvement in adhesion compared to the STR control; some samples were so adherent that they did not initiate peel, even after 775 h exposure to damp heat [3]. The most promising primers are being compounded into EVA for further testing.

NREL-prepared alternate encapsulant formulations were also tested. These included EVA and an ethylene copolymer of methacrylate with glycidyl functional groups having various silanes incorporated into the base resin. Some materials were found to be similar or inferior in performance to STR's 15295P EVA. One material was quite promising; no peel initiation occurred after 743 h damp heat exposure.

3.2 Backsheets

Backsheet candidates include NREL plasma-enhanced chemical vapor deposition (PE-CVD) coated PET films [4], three commercial products from Isovolt, an experimental laminate from DuPont Teijin Films, ten PE-CVD coated PET samples from AKT, two multi-layer coated PET samples from PNNL, and an uncoated/unlaminated liquid crystal polymer (LCP). The various samples are at different stages of evaluation. Water vapor permeability was measured as a function of temperature (see Fig. 1). LCPs have very low permeability values, typically 100 times lower than uncoated PET. LCPs also provide a better moisture barrier than experimental PET films having inorganic coatings, although the sample of LCP has a higher

activation energy than either the coated or uncoated PET film. However, the LCP material by itself is very fragile and may be better suited for use in a laminate construction; it is also a relatively expensive material. Polyethylene naphthalate (PEN) has been identified as a high-performance material for the food packaging industry. Although it does have better moisture barrier properties than PET, the water vapor transmittance rate (WVTR) of uncoated PEN is inadequate for PV applications. The Isovolt Tedlar-SiOx-PET backsheets exhibit barrier properties intermediate between uncoated PET and some experimental oxide/nitride coated PET films.

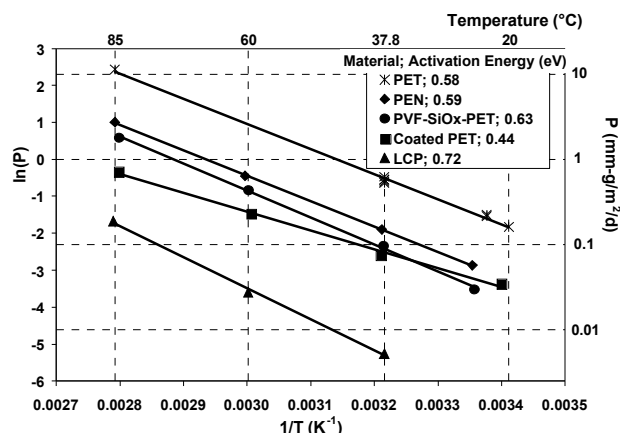


Figure 1. Arrhenius plot of permeability for backsheets at 85% RH

3.3 Combined Packaging

Several experiments were performed to evaluate the relative effectiveness of various packaging strategies and components (e.g., backsheets, encapsulants, edge sealants) in preventing moisture-induced degradation of thin-film devices. The performance of small (laboratory scale) PV devices is difficult to characterize without compromising the integrity of the protective package. However, exposure to damp heat (85°C/85% RH) aggressively corrodes aluminum, which is often used in PV modules (e.g., as interconnects). Consequently, thin-film aluminum coatings were vacuum deposited onto glass substrate test articles to simulate a PV device and provide a rapid visual indication of damage. The extent of degradation as a function of exposure time was documented with digital imagery. A number of backsheet/encapsulant combinations were laminated to the aluminized glass and were subjected to 1000 hours of damp heat exposure.

Samples with the TPE breathable backsheet provided very good protection of the Al layer. Substantial bulk corrosion of Al occurred for glass/EVA/Al-glass samples, suggesting that corrosion of the Al may be catalyzed by by-products (possibly acetic acid) within the encapsulant. Samples with the BRP-C encapsulant exhibited excellent

protection of the aluminum layer, independent of the type of backsheet. Samples with the experimental DuPont Teijin backsheet did not exhibit aluminum corrosion, even though its adhesion to EVA was severely compromised by damp heat exposure. If this problem could be eliminated, this material would be an attractive advanced backsheet because the WVTR at 85°C/100% RH is below the measurement sensitivity of our MOCON instrument. Properly wetted edge seal materials demonstrated an outstanding ability to prevent moisture ingress in glass/glass constructions, even when a bead-blasted edge delete exists.

4. Conclusions

We have evaluated a large number of backsheet and encapsulant materials in terms of their moisture barrier properties and their ability to maintain good adhesion during damp heat exposure. Several promising packaging candidates have been identified. Additional efforts to develop improved encapsulants (by compounding high-potential primers into EVA for further testing) and backsheets (by deposition of high barrier coatings onto polymer films) are ongoing. We have also investigated the effectiveness of several combined packaging strategies/constructions to provide increased protection of PV modules. Glass/glass laminate constructions with EVA are believed to trap harmful compounds that catalyze moisture-driven corrosion of aluminum. Constructions with breathable backsheets allow higher rates of moisture ingress, but also allow egress of deleterious substances, thereby reducing corrosion.

REFERENCES

- [1] *Solar Energy Technologies Program Multi-Year Technical Plan, 2003-2007 and Beyond*, DOE/GO-102004-1775, U.S. Department of Energy, Washington DC, January 2004.
- [2] M.D. Kempe, "Control of Moisture Ingress into Photovoltaic Modules," *Proc. of the 31st IEEE PV Specialists Conference, 2005, Lake Buena Vista, FL* (to be published).
- [3] J.F. Pern, and G.J. Jorgensen, "Enhanced Adhesion of EVA Laminates to Primed Glass Substrates Subjected to Damp Heat Exposure," *Proc. of the 31st IEEE PV Specialists Conference, 2005, Lake Buena Vista, FL* (to be published).
- [4] S.H. Glick et al., "Dielectric Thin-Film Barriers of Silicon Oxynitride for Protecting Photovoltaic Cells and Modules," *Proc. of the 31st IEEE PV Specialists Conference, 2005, Lake Buena Vista, FL* (to be published).

REPORT DOCUMENTATION PAGE				<i>Form Approved</i> <i>OMB No. 0704-0188</i>	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.					
1. REPORT DATE (DD-MM-YYYY) January 2005		2. REPORT TYPE Conference Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Packaging Materials and Design for Improved PV Module Reliability				5a. CONTRACT NUMBER DE-AC36-99-GO10337	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) G. Jorgensen, K. Terwilliger, M. Kempe, J. Pern, S. Glick, J. del Cueto, C. Kennedy, and T. McMahon				5d. PROJECT NUMBER NREL/CP-520-36835	
				5e. TASK NUMBER PVP37201	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				8. PERFORMING ORGANIZATION REPORT NUMBER NREL/ CP-520-36835	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S) NREL	
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER	
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT (Maximum 200 Words) A number of candidate alternative encapsulant and soft backsheet materials have been evaluated in terms of their suitability for photovoltaic (PV) module packaging applications. Relevant properties, including peel strength as a function of damp heat exposure and permeability, have been measured. Based on these tests, promising new encapsulants with adhesion-promoting primers have been identified that result in improved properties. Test results for backsheets provided by industry and prepared at the National Renewable Energy Laboratory (NREL) have suggested strategies to achieve significantly improved products. The ability of glass/glass and glass/breathable backsheet constructions laminated with various encapsulant and/or edge seal materials to protect thin-film aluminum coatings deposited onto glass substrates was assessed. Glass/glass laminate constructions can trap harmful compounds that catalyze moisture-driven corrosion of the aluminum. Constructions with breathable backsheets allow higher rates of moisture ingress, but also allow egress of deleterious substances that can result in decreased corrosion.					
15. SUBJECT TERMS PV; concentrating solar power; module packaging applications; glass/breathable backsheet; thin-film aluminum coatings;					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)